

Effect of Sodium Tripolyphosphate on Polished and Roughened Bovine Enamel

Wang, Changxiang; Cooper, Paul; Smith, Anthony

License:

Creative Commons: Attribution (CC BY)

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Wang, C, Cooper, P & Smith, A 2017, 'Effect of Sodium Tripolyphosphate on Polished and Roughened Bovine Enamel', *Journal of Internal Medicine & Primary Healthcare*. <<http://www.heraldopenaccess.us/fulltext/Internal-Medicine-&-Primary-Healthcare/Effect-of-Sodium-Tripolyphosphate-on-Polished-and-Roughened-Bovine-Enamel.php>>

[Link to publication on Research at Birmingham portal](#)

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Research Article

Effect of Sodium Tripolyphosphate on Polished and Roughened Bovine Enamel

Changxiang Wang^{1*}, Robert Lucas², Paul R Cooper¹ and Anthony J Smith¹

¹School of Dentistry, University of Birmingham, 5 Mill Pool Way, Edgbaston, Birmingham, UK

²GlaxoSmithKline Consumer Healthcare, St. George's Avenue, Weybridge, UK

Abstract

Objectives: Sodium Tripolyphosphate (STP) is commonly incorporated into toothpastes for stain removal where its mild chelating properties interfere with stained pellicle integrity. However, these chelating properties may negatively impact on enamel surface finish. This study investigated the effects of STP treatment on the surface finish of polished and roughened enamel with and without tooth-brushing.

Methods: Bovine enamel specimens (n=8/group) were prepared to either 1200-grit SiC and 3µm diamond finish (Polished group), P800-ground finish, or P320-ground finish and soaked or brushed (Oral B P35), using an *in vitro* tooth-brushing simulator (5-60m brushing), in STP solutions of concentrations (w/w) 2.5%, 5.0% or 10.0% STP. Gloss changes were measured with a Novo-Curve glossmeter and surface roughness and wear depth determined by profilometry.

Results: There were no significant changes in surface roughness and wear depth after brushing in STP for 5-60m. Small gloss decreases occurred for all polished and roughened specimens, which were of greater magnitude with prolonged soaking or brushing. Brushing in STP did not exacerbate the gloss loss relative to soaking for equivalent times. There was no clear linear relationship between STP concentration and gloss change after soaking or brushing reflecting the small gloss changes taking place.

Conclusion: Minor decreases in enamel surface gloss following extensive soaking in STP did not cause greater susceptibility to wear during tooth-brushing. Only minimal changes in enamel surface finish occurred after exposure to STP, even with highly polished surfaces, and its stain removal properties potentially provide positive benefits for oral hygiene.

Keywords: Cleaning; Enamel; Gloss; Oral hygiene ; Sodium tripolyphosphate; Surface roughness; Wear

*Corresponding author: Changxiang Wang, School of Dentistry, University of Birmingham, 5 Mill Pool Way, Edgbaston, Birmingham B5 7EG, UK; Tel: +44 1214665528; Fax: +44 1214665491; E-mail : c.wang@bham.ac.uk

Citation: Wang C, Lucas R, Cooper PR, Smith AJ (2017) Effect of Sodium Tripolyphosphate on Polished and Roughened Bovine Enamel. J Gen Pract Med Diagn 2: 004.

Received: November 9, 2016; **Accepted:** January 19, 2017; **Published:** February 07, 2017

Introduction

Effective cleaning of the tooth surface through good oral hygiene is central to both the prevention of oral and dental disease and the appearance of the dentition. Clear causal links are well established between the presence of dental plaque, caries and periodontal disease. The appearance of the teeth, particularly whiteness, is of great importance to patients and tooth discolouration is a common dental complaint. It has been reported, depending on the population examined, that personal dissatisfaction with the appearance of the dentition ranges from 17.9 to 52.6% [1-5]. Extrinsic staining of the tooth can arise from a variety of sources including smoking, red wine consumption, cationic compounds such as chlorhexidine or stannous salts [6-9]. Stain removal can be challenging, thus, oral hygiene strategies need to address both the removal of dental plaque and extrinsic stain.

While a variety of tooth whitening procedures are used professionally [10-13], they are costly and labour intensive [14], and some of these procedures do not contribute to oral hygiene. There is considerable demand for 'Over-The-Counter' (OTC) tooth-whitening products that can be integrated into a normal oral hygiene regime, and whitening toothpastes are the dominant delivery format [15]. In general, whitening toothpastes provide tooth whitening by abrasive removal of extrinsic stain and dental plaque and the chemical action of constituents such as Sodium Tripolyphosphate (STP), sodium pyrophosphate, sodium hexametaphosphate, hydrogen peroxide, as well as the enzymes papain and bromelain [3].

Sodium Tripolyphosphate (STP) is a linear condensed phosphate that is commonly incorporated in whitening toothpastes for effective stain removal [16], where its mild chelating properties interfere with stained pellicle integrity [17-19]. However, increasing interest in enamel surface finish and polishing raises questions as to whether these chelating properties may negatively impact enamel surface finish. There are not many studies in the literature regarding the effect of STP on the surface roughness and gloss at varying concentrations. The present *in vitro* study investigates the effects of STP treatment on the surface finish of polished and roughened bovine enamel, with and without tooth brushing.

Materials and Methods

Effects of STP on enamel without tooth brushing

Bovine enamel (Modus Laboratories, UK) specimens (approximate 18mm × 12mm) were prepared from tooth crowns by dissection using a diamond-edged saw and embedded in blocks of epoxy resin (Ø25 mm) (Buehler, UK). Eight bovine enamel specimens per treatment group were prepared flat (approximate 12mm × 6mm exposed area) to either; a) 1200-grit SiC and 3 µm diamond finish (Polished group), b) P800 ground finish, or c) P320 ground finish with 5 minutes ultrasonication in water following each treatment. A Phoenix Beta Grinder/Polisher (Buehler, UK) was used with SiC abrasive discs (Buehler, UK) for sample preparation. The polishing sequence includes grinding the specimens by using coarse SiC abrasive discs, then 1200-grit SiC and 3 µm diamond polishing. Specimens were soaked sequentially for

0.5, 1, 5, 10, 30 and 60 minutes in STP solutions with gentle agitation. The specimens were washed with tap water after soaking and gloss measurements were taken before and after treatment with a Novo-Curve small area glossmeter (Rhopoint Instrumentation Ltd. England), at intervals of 90 degrees rotation about the centre point of each specimen. Three concentrations of STP (PRAYON, Belgium), i.e., 2.5 w/w %, 5.0 w/w % and 10.0 w/w % were used and water was used as a negative control.

Effect of STP on enamel with tooth brushing

Eight bovine enamel specimens per treatment group were prepared flat (approximate 12mm × 6mm exposed area) to either; a) 1200-grit SiC and 3 μm diamond finish (Polished group), b) P800 ground finish, or c) P320 ground finish with 5 minutes ultrasonication in water following each treatment, and then surface profiled (Talysurf Series 2 inductive gauge profilometer, Taylor-Hobson, UK). A Phoenix Beta Grinder/Polisher (Buehler, UK) was used with SiC abrasive discs (Buehler, UK) for sample preparation. The polishing sequence includes grinding the specimens by using coarse SiC abrasive discs, then 1200-grit SiC and 3 μm diamond polishing. ADA/ISO standard tape was used to cover the unbrushed reference area and only a test band of the enamel specimen (approximate 12mm × 6mm area) was exposed. Compared with the brushed area, only a relatively small un-brushed area was covered with a standard tape as the reference surface. The enamel specimens were mounted in two brushing channels of an *in vitro* brushing simulator [20]. Oral B P35 toothbrushes were used for the brushing. Specimens were double brushed sequentially for 5 mins (600 strokes), 10 mins (1200 strokes), 30 mins (3600 strokes) and 60 mins (7200 strokes) at a brushing speed of 120 rpm and a temperature of 20°C was maintained throughout the whole brushing procedure. Three concentrations of STP, i.e., 2.5 w/w %, 5.0 w/w % and 10.0 w/w % were used. 150g STP solution was used in each channel and a brushing load of 150 g was applied. After brushing for the requisite number of strokes, the tape was removed and any residue cleared by gently wiping with a wet tissue before thorough rinsing with water.

Linear profiles (2D) were taken of the brushed specimen surfaces using a Talysurf Series 2 inductive gauge profilometer (Taylor-Hobson, UK), and wear depth and roughness values were calculated using Talysurf software and 3D surface analysis of selecting specimens was conducted. Gloss measurements were taken before and after brushing with a Novo-Curve small area glossmeter, at intervals of 90 degrees rotation about the centre point of each specimen.

Statistical analysis of the data

Data were analysed by single factor ANOVA with a significance level of $p \leq 0.05$.

Results

Effect of STP on enamel without tooth-brushing

The mean gloss changes for the polished and roughened bovine enamel surfaces showed small decreases in gloss for both polished and roughened bovine enamel specimens and the gloss decreases were greater in magnitude with longer soaking times (Figure 1a-c).

Statistically significant differences were detected between all the exposure time points for gloss change with polished finish specimens for the three STP concentrations, while no significant differences were detected after 5 min exposure for P800 ground, and after 30 min exposure for P320 ground finish specimens. Single factor ANOVA showed

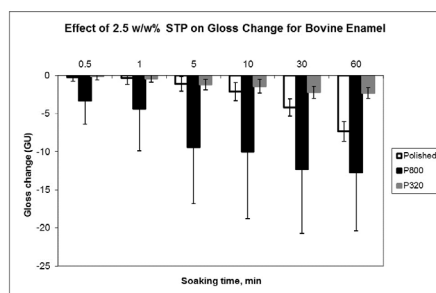


Figure 1 (a)

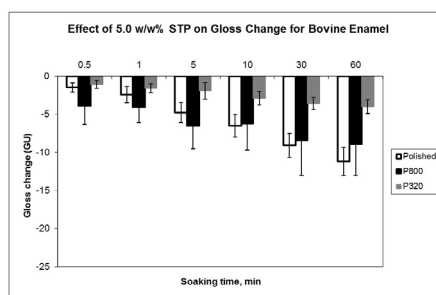


Figure 1 (b)

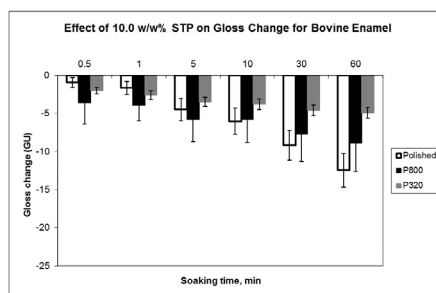


Figure 1 (c)

Figure 1: Gloss changes for bovine enamel surfaces after soaking (a-c).

that no significant differences were detected between the STP concentrations for gloss change with P800 ground finish at the same exposure time points. At the same exposure time point significant differences were found for gloss change with polished and P320 ground finish surfaces between the STP concentrations except between the concentrations of 5.0% (w/w) and 10.0% (w/w) with polished finish. No clear trend was found between the three surface treatments (polished, P800 ground and P320 ground) for gloss change with exposure to the three STP concentrations. There were no observed gloss changes when the polished enamel specimens were soaked in water. Neither the surface finish of the specimens nor the concentration of STP solution in which the specimens were soaked had appreciable influence on the level of gloss change perhaps reflecting the small changes observed.

Effect of STP on enamel with tooth-brushing

Small decreases in gloss were observed for all the polished and roughened bovine enamel specimens following brushing with STP (Figure 1d-f).

The magnitude of these gloss changes was relatively small even after 60 mins (7200 strokes) brushing and increased with increasing number of brushing strokes. The changes in gloss were most apparent for the specimens with polished enamel surfaces, although STP

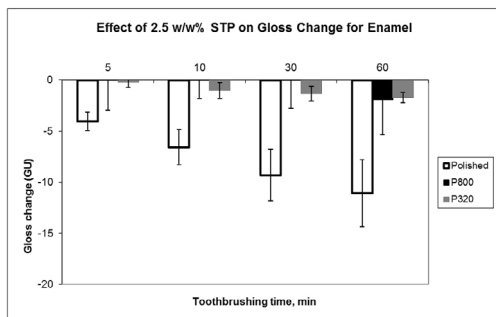


Figure 1 (d)

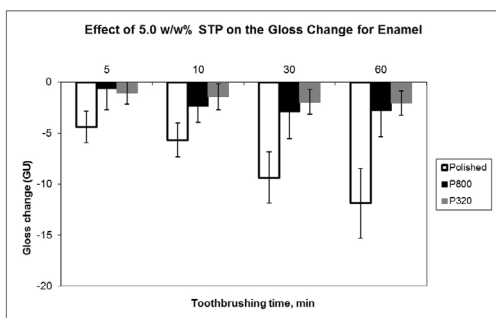


Figure 1 (e)

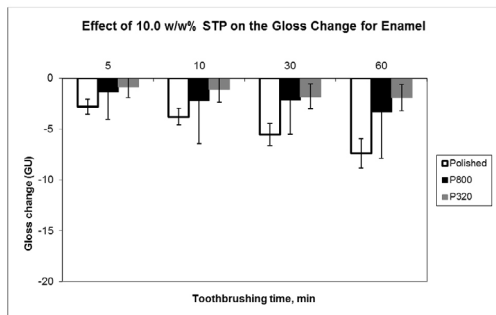


Figure 1 (f)

Figure 1: Tooth-brushing (d-f) with STP.

concentration did not appear to influence gloss change for P800 ground and P320 ground specimens (no significant differences were detected between the STP concentrations using the same number of brushing strokes). Single factor ANOVA showed that no statistically significant differences were present between P800 ground and P320 ground finish specimens when brushing with the same STP concentration and the same number of brushing strokes, while significant differences were detected between the polished and P800 ground and polished and P320 ground specimens.

The mean surface roughness for the polished and roughened bovine enamel surfaces did not change following brushing for up to 60 mins (7200 strokes) and STP concentration had no influence on this parameter (Figure 2a-c).

Profilometric assessment of wear depth indicated that this was at the limit of accurate resolution (approximately 0.05 microns or less) for all specimens and did not change with brushing time or STP concentration (data not shown).

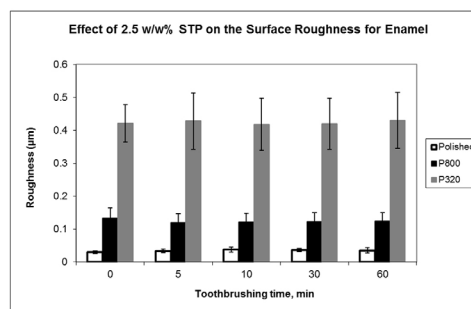


Figure 2 (a)

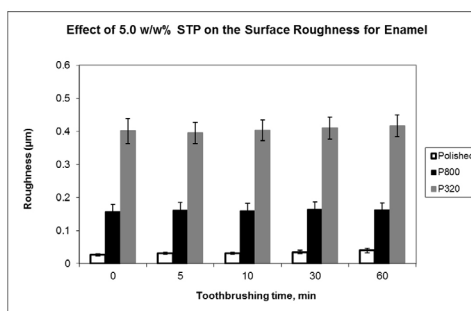


Figure 2 (b)

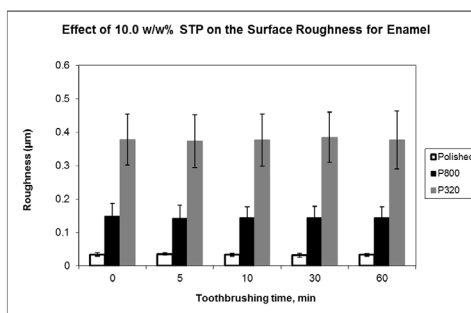


Figure 2 (c)

Figure 2: Surface roughness for bovine enamel surfaces after tooth-brushing with STP.

Discussion

Bovine enamel has been used in this pilot study due to the reported and extensive similarities between bovine and human teeth. Indeed a recent study, which compared teeth from several species, indicated that on the basis of their chemical and morphological composition, bovine teeth should be the first choice as substitutes for human teeth in research [21].

Sodium tripolyphosphate, a sodium salt of triphosphoric acid, has been widely used for water treatment, detergency and in the food industry [22,23]. Its surfactant and chelating properties have led to its use in whitening toothpastes for stain removal. *In vitro* studies with crystalline Hydroxyapatite (HA) powder showed that STP was effective in removing existing stain and inhibiting stain formation through inhibition of the adsorption of salivary protein or tea stain and the desorption of existing protein and stain from HA surfaces [15,24]. *In vivo* trials also reported significant extrinsic stain removal efficacy for a dentifrice containing STP versus the baseline [18] and a reduction in dental stain by a chewing gum containing STP [25]. These beneficial

effects for stain removal and inhibition depend in part on the chelating properties of STP, the latter of which may, however, negatively impact on enamel surface finish.

In the present study, the effects of STP on several parameters of enamel surface finish have been examined to determine whether its chelating properties have any adverse effects. Furthermore, exposure of enamel to STP has been investigated both by simple soaking of specimens in STP solutions and also, following tooth-brushing with STP solutions under clinically relevant exposure time conditions. Any significant chelating action of STP may be expected to show exaggerated enamel surface loss when exposure occurs under brushing conditions due to the physical abrasion from brushing on a softened surface. Surface gloss of enamel represents a very sensitive parameter of change to the surface finish of this tissue. Soaking or brushing of enamel specimens in STP for periods of 5 – 60 mins resulted in only small decreases in surface gloss, with little difference between the two treatments, suggesting that any chelating action of STP caused minimal tissue loss from the enamel surface. Both surface roughness and wear depth values did not show any change after exposure of specimens to STP for up to 60 mins. The starting finish of an enamel surface (polished vs ground) influences its available surface area, but the lack of influence of this on gloss, surface roughness or wear depth emphasizes the minimal effects of STP on enamel surface finish, as does the lack of influence of STP concentration. Interestingly, a lack of influence of STP concentration on stain desorption from hydroxyapatite has also been reported [24].

Mechanistically, it has been suggested that the main action of STP in both the inhibition of salivary protein adsorption to hydroxyapatite and desorption of bound salivary proteins is through competitive binding to the crystal surface, although the chelating action of STP has been proposed as a possible additional factor [24]. Data from the present study indicate that chelating effects of STP on intact enamel are minimal under clinically relevant exposure times, implying that chelation may be of minor importance when considering adsorption/desorption of salivary proteins and stains to enamel.

In summary, the present study has demonstrated that exposure of enamel to STP, either by soaking or with brushing, results in only minimal changes to surface gloss and has no statistically significant effect on surface roughness or wear depth. Thus, several parameters of enamel surface finish indicate that any chelating action of STP on enamel is minimal under clinically relevant conditions underpinning the positive benefits from its use for stain removal from teeth.

Acknowledgement

The authors gratefully acknowledge financial support from GSK Consumer Healthcare for this research.

Competing interest

The authors are not aware of any competing interests for this study.

References

1. Joiner A (2010) Whitening toothpastes: A review of the literature. J Dent 38: 17-24.
2. Alkhatib MN, Holt R, Bedi R (2004) Prevalence of self-assessed tooth discoloration in the United Kingdom. J Dent 32: 561-566.
3. Alkhatib MN, Holt R, Bedi R (2005) Age and perception of dental appearance and tooth colour. Gerodontology 22: 32-36.
4. Xiao J, Zhou XD, Zhu WC, Zhang B, Li JY, et.al. (2007) The prevalence of tooth discoloration and the self-satisfaction with tooth colour in a Chinese urban population. J Oral Rehabil 34: 351-360.
5. Odioso LL, Gibb RD, Gerlach RW (2000) Impact of demographic, behavioural, and dental care utilization parameters on tooth colour and personal satisfaction. Compend Contin Educ Dent Suppl 21: 35-41.
6. Joiner A (2006) Review of the extrinsic stain removal and enamel/dentine abrasion by a calcium carbonate and perlite containing whitening toothpaste. Int Dent J 56: 175-180.
7. Watts A, Addy M (2001) Tooth discoloration and staining: a review of the literature. Br Dent J 190: 309-316.
8. Ten Bosch JJ, Coops JC (1995) Tooth colour and reflectance as related to light scattering and enamel hardness. J Dent Res 74: 374-380.
9. Nathoo SA (1997) The chemistry and mechanisms of extrinsic and intrinsic discoloration. J Am Dent Assoc 128: 6-10.
10. Joiner A (2006) The bleaching of teeth: A review of the literature. J Dent 34: 412-419.
11. Griffiths CE, Bailey JR, Jarad FD, Youngson CC (2008) An investigation into most effective method of treating stained teeth: An *in vitro* study. J Dent 36: 54-62.
12. Sarrett DC (2002) Tooth whitening today. J Am Dent Assoc 133: 1535-1538.
13. Lynch CD, McConnell RJ (2003) The use of microabrasion to remove discoloured enamel: A clinical report. J Prosthet Dent 90: 417-419.
14. Walsh TF, Rawlinson A, Wildgoose D, Marlow I, Haywood J, et.al. (2005) Clinical evaluation of the stain removal ability of a whitening dentifrice and stain controlling system. J Dent 33: 413-418.
15. Langford J, Pavey KD, Olliff CJ, Cragg PJ, Hanlon GW, et.al. (2002) Real-time monitoring of stain formation and removal on calcium hydroxyapatite surfaces using quartz crystal sensor technology. Analyst 127: 360-367.
16. American Dental Association (2001) Whitening toothpastes. Journal of the American Dental Association 132: 1146-1147.
17. Sharif N, MacDonald E, Hughes J, Newcombe RG, Addy M (2000) The chemical stain removal properties of whitening toothpaste products: studies *in vitro*. Br Dent J 188: 620-624.
18. Hughes N, Maggio B, Sufi F, Mason S, Kleber CJ (2009) A comparative clinical study evaluating stain removal efficacy of a new sensitivity whitening dentifrice compared to commercially available whitening dentifrice. J Clin Dent 20: 218-22.
19. Soparkar P, Rustogi K, Zhang YP, Petrone ME, DeVizio W, et.al. (2004) Comparative tooth whitening and extrinsic tooth stain removal efficacy of two tooth whitening dentifrices: six-week clinical trial. J Clin Dent 15: 46-51.
20. Parry J, Harrington E, Rees GD, McNab R, Smith AJ (2008) Control of brushing variables for the *in vitro* assessment of toothpaste abrasivity using a novel laboratory model. J Dent 36: 117-124.
21. Teruel JD, Alcolea A, Hernández A, Ruiz AJ (2015) Comparison of chemical composition of enamel and dentine in human, bovine, porcine and ovine teeth. Arch Oral Bio 60: 768-775.
22. Rashchi F, Finch JA (2000) Polyphosphates: A review. Their chemistry and application with particular reference to mineral processing. Minerals Engineering 13: 1019-1035.
23. Hourant P (2004) General properties of the alkaline phosphates: major food and technical applications. Phosphorus Research Bulletin 15: 85-94.
24. Shellis RP, Addy M, Rees GD (2005) *In vitro* studies on the effect of sodium tripolyphosphate on the interactions of stain and salivary protein with hydroxyapatite. J Dent 33: 313-324.
25. Porciani PF, Perra C, Grandini S (2010) Effect on dental stain occurrence by chewing gum containing sodium tripolyphosphate—a double-blind six-week trial. J Clin Dent 21: 4-7.